

AD-A193 985

MEASUREMENT OF Li^+ ION TRANSPORT NUMBERS IN PED-LIX
COMPLEXES(U) MINNESOTA UNIV MINNEAPOLIS CORROSION
RESEARCH CENTER M Z MUNSHI ET AL. MAR 88

171


UNCLASSIFIED

N00014-85-C-1588

F/G 7/2

NL



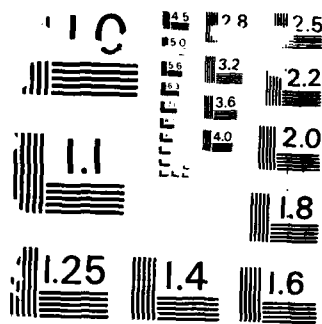

COPY RESOLUTION TEST CHART
NATIONAL BUREAU OF STANDARDS-1963-A

Polymer Journal: Regular Article

FILE COPY

AD-A193 985

Measurement of Li^+ Ion Transport
Numbers in PEO-LiX Complexes

M.Z.A. Munshi

B.B. Owens

S. Nguyen

Department of Chemical Engineering and Materials Science
Corrosion Research Center
University of Minnesota
Minneapolis, MN 55455

DTIC
ELECTE
APR 27 1988
S D
RH

(Running Head: Li Ion Transport Number)

Abstract

The transport number for Li^+ ions in PEO-LiX complexes was measured using a potentiostatic polarization technique. The results indicate that the Li^+ ion transport is strongly influenced by the salt concentration and the type of counter ions.

KEY WORDS: Transport Number/Polyethylene Oxide/Salt/Polarization/
Lithium

DISTRIBUTION STATEMENT A
Approved for public release,
Distribution Unlimited

88 4 26 150

A192 985

SECURITY CLASSIFICATION OF THIS PAGE

REPORT DOCUMENTATION PAGE

1a. REPORT SECURITY CLASSIFICATION Unclassified			1b. RESTRICTIVE MARKINGS	
2a. SECURITY CLASSIFICATION AUTHORITY			3. DISTRIBUTION/AVAILABILITY OF REPORT	
2b. DECLASSIFICATION/DOWNGRADING SCHEDULE			Unclassified/Unlimited	
4. PERFORMING ORGANIZATION REPORT NUMBER(S) ONR Technical Report 16			5. MONITORING ORGANIZATION REPORT NUMBER(S)	
6a. NAME OF PERFORMING ORGANIZATION Corrosion Research Center	6b. OFFICE SYMBOL (if applicable)	7a. NAME OF MONITORING ORGANIZATION Office of Naval Research, Resident Rep.		
6c. ADDRESS (City, State, and ZIP Code) University of Minnesota Minneapolis, MN 55455		7b. ADDRESS (City, State, and ZIP Code) Federal Building, Room 286 536 South Clark Street Chicago, IL 60605-1588		
8a. NAME OF FUNDING/SPONSORING ORGANIZATION Office of Naval Research	8b. OFFICE SYMBOL (if applicable) Code 1113	9. PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER Contract No. N00014-85-1588		
8c. ADDRESS (City, State, and ZIP Code) 800 North Quincy Street Arlington, VA 22217-5000		10. SOURCE OF FUNDING NUMBERS		
		PROGRAM ELEMENT NO.	PROJECT NO.	TASK NO.
		WORK UNIT ACCESSION NO.		
11. TITLE (Include Security Classification) Measurement of Li ⁺ Ion Transport Numbers in PEO-LiX Complexes				
12. PERSONAL AUTHOR(S) M.Z.A. Munshi, R.R. Owens, S. Nguyen				
13a. TYPE OF REPORT Technical	13b. TIME COVERED FROM 7/15/85 TO 1/88	14. DATE OF REPORT (Year, Month, Day) March 1988	15. PAGE COUNT 16	
16. SUPPLEMENTARY NOTATION Submitted for publication in Polymer Journal, 1988.				
17. COSATI CODES			18. SUBJECT TERMS (Continue on reverse if necessary and identify by block number)	
FIELD	GROUP	SUB-GROUP	Transport Number/Polyethylene Oxide/Salt/Polarization/ Lithium	
19. ABSTRACT (Continue on reverse if necessary and identify by block number) The transport number for Li ⁺ ions in PEO-LiX complexes was measured using a potentiostatic polarization technique. The results indicate that the Li ⁺ ion transport is strongly influenced by the salt concentration and the type of counter ions.				
20. DISTRIBUTION/AVAILABILITY OF ABSTRACT <input checked="" type="checkbox"/> UNCLASSIFIED/UNLIMITED <input type="checkbox"/> SAME AS RPT. <input type="checkbox"/> OTC USERS			21. ABSTRACT SECURITY CLASSIFICATION Unclassified	
22a. NAME OF RESPONSIBLE INDIVIDUAL Boone B. Owens			22b. TELEPHONE (Include Area Code) (612) 625-1332	22c. OFFICE SYMBOL

1. INTRODUCTION

Lithium ion conducting polymer materials are being intensively investigated in a number of research laboratories because of their potential use as solid electrolytes in high energy density solid state lithium batteries. The most widely used polymer has been based on polyethylene oxide (PEO). The conduction mechanism in these polymer electrolytes has generally been assumed to be due to Li^+ ion transport from one lone pair site to another along the helical PEO strands. However, recent studies have shown that the Li^+ transport number is less than unity.

The mechanism of ion transport in these polymer electrolytes remains an important issue and despite numerous studies its modus operandi therein is not well understood.

In a previous study,⁸ it was found that the ionic conductivity of the PEO-LiX system was strongly influenced by the salt concentration and anion type. A model was proposed whereby the decrease in the ionic conductivity with increasing salt concentration was due to ion-pair formation. In addition, there was an empirical relationship between the anion size and conductivity. The present study involving the measurement of transport numbers of the cations and anions in these polymer electrolytes was undertaken to clarify some of the addressed issues.

n For	
A&I	<input checked="checked" type="checkbox"/>
ed	<input type="checkbox"/>
Distribution	
Distribution/	
Availability Codes	
Avail and/or	Special
Dist	
A-1	

A number of methods have been used to measure the transport number of Li^+ ions in polymer electrolytes with quite diverse results. This may be due to the technique not being sound for this type of electrolyte. The transport of cations and anions through the electrolyte involves a number of parameter changes, viz, ionic mobility of cations and anions, conductivity of electrolyte, cation-anion interactions, and motions of PEO molecules in the electrolyte. These parameters vary for different salt concentrations, temperature and molecular weight of the PEO electrolyte. Hence it is not surprising to find that conventional methods of measuring transport numbers in such polymer electrolytes appear to be inapplicable. The use of dilute solution theory to explain ion transport phenomena is inadequate for such complex systems. In addition, concentrated solution theory is not well developed for polymer electrolytes. Until these phenomena are better understood, a compromise has to be made on the measurement techniques.

Clearly the classical Tubandt method is unsuitable because at elevated temperatures, the electrolyte layers fuse to one another. More recently, a.c. impedance techniques have been used to determine the transport number of the lithium cation in polymer electrolytes. This is carried out in the diffusion region at very low frequencies (<1 Hz). At such low frequencies, the techniques reduce to one involving potentiostatic polarization described by Shriver, et al.,⁹. It is not unreasonable, thus, to obtain comparable results using the two

techniques¹⁰. The method developed by Shriver relies solely on the initial and final state and any intermediate state is ignored.

This technique was used in this paper to determine the transport number of lithium ions in PEO-LiX electrolytes and the results discussed in relation to ion transport phenomena.

2. EXPERIMENTAL

The preparation of the polymer electrolyte films using five different salts and six different PEO-LiX compositions have been described elsewhere⁸. The salts under study were LiCF_3SO_3 , LiAlCl_4 , LiAsF_6 , LiBF_4 and LiPF_6 and the PEO-LiX concentrations were 50:1, 25:1, 8:1, 4:1, 2:1 and 1:1. All subsequent handling of the films and cell manipulation were carried out in the glove-box.

A two electrode cell, reversible to one of the ions in the electrolyte (namely Li) was used to determine the transport number (Figure 1). A constant voltage of 50 mV was applied across the cell and the current flow measured as a function of time. Under the applied load, cations migrate to the negative electrode and anions to the counter electrode. This leads to a salt concentration gradient across the electrolyte. As the cell polarizes, a depletion of salt concentration results near the negative electrode with concurrent increase near the positive electrode. The current decreases to a steady state when the back emf created by the concentration gradient

exactly opposes the applied potential. A plateau results in the I-t curve since cations are now the only species carrying the current. The ratio of the steady state current to the initial current gives the transport number for the cation. Due to rapid polarization, the initial current was calculated from the total cell impedance determined by a.c. methods and the applied d.c. potential. In some cases measurements were made using three different thicknesses of electrolytes to determine the variability in the result. The temperature range studied was 70-120°C.

3. RESULTS AND DISCUSSIONS

A typical variation in the cell current with time under an applied d.c. potential is shown in Figure 2. At high potentials (100mV-1V) current values were not "steady" probably because concentration polarization prevailed over steady state.

Figure 3 shows the variation in the transport number of the Li^+ cation against concentration of various lithium salts in PEO. As shown, the transport number changes dramatically with composition. During the potentiostatic polarization, the composition gradient means that the transport number across the cell varies. We observe an "averaged" value. At low salt concentration, the transport number values are high indicating a high degree of solvation of the Li^+ cation by the oxygen lone pairs of electrons from the PEO. As the salt concentration in PEO increases, the number of lithium ions occupying

the lone pairs increases until saturation is reached. This corresponds to an increase in the transport number value indicated by a maximum on the curve. Further increase in salt concentration results in a decrease in transport number. This suggests the formation of ion-pairs. As the number of free PEO segments decreases, the subsequent formation of ion-pairs hinders the motion of Li^+ ions, resulting in a decrease in the ionic mobility of Li^+ . These results are in excellent confirmation with the a.c. conductivity data which suggest a decrease in the ionic conductivity of the polymer electrolyte with increasing salt concentration. The constancy in the values of the transport number at the higher salt concentration range suggest the formation of multiplets.

Figure 4 shows the variation in the transport number of the Li^+ ion versus the sum of the ionic radius⁸ of the cations and anions for the various salts under study at 100°C . The trend is as expected with the transport number value being highest for the LiAsF_6 salt. Since the energy required to separate the ions is proportional to the inverse of their ionic radii, considerably less ionic interaction takes place in the case of the larger AsF_6^- anion. Beyond this size, it is believed that steric hindrance dominates which introduces strong electrostatic repulsive forces among the Li^+ ions thus reducing its mobility.

Figure 5 shows the variation of Li^+ transport number with

temperature in various PEO-LiX electrolytes at a fixed O:Li concentration of 8:1. In the case of the PEO-LiAlCl₄, PEO-LiAsF₆ and PEO-LiPF₆ system, the transport number was found to increase somewhat with temperature. In the other two systems investigated the transport number was found to be temperature independent. The dependence on temperature suggests that the activation energy for cation transport is greater than for anion transport. This probably results because the cation-anion interaction is considerably less due to the larger anion size. It follows that the mobility of the cation is relatively higher than that of the anion.

In the case of smaller anions such as CF₃SO₃⁻ and BF₄⁻, the cation-anion interaction is much larger and the mobility of the cation approaches that of the anion. This suggests that the activation energy for cation and anion transport are about the same. This leads to a curve which is temperature independent.

The above observations are consistent with the model proposed in an earlier study. The transport number of the Li⁺ ion was also determined using three electrolyte thickness. The results shown in Table 1 suggest that in the range studied, the transport number is independent of thickness.

ACKNOWLEDGEMENT

The authors should like to acknowledge Dr. J.Y. Cherng for many

helpful discussions.

This was supported in part by the Office of Naval Research.

REFERENCES

1. R. Dupon, D.H. Whitmore and D.F. Shriver, J. Electrochem. Soc., 128, 715 (1981).
2. A.V. Chadwick, J.H. Strange and M.R. Worboys, Proc. 4th Int. Conf. on Solid State Ionics, Grenoble, France, (North-Holland, Amsterdam), 1155 (1983).
3. M. Armand, J.M. Chabagno and M.J. Duclot, Abst. Second Int. Meeting on Solid Electrolytes, St. Andrews, Scotland, Abst. #65, (1978).
4. P.R. Sorensen and T. Jacobsen, Electrochim. Acta, 27, 1671 (1982).
5. R. Dupon, B.L. Papke, M.A. Ratner and D.F. Shriver, J. Electrochem. Soc., 131, 586 (1984).
6. M. Leveque, J.F. LeNest, A. Gandini and H. Cheradame, Makromol. Chem. Rapid Commun. 4, 497 (1983).
7. M. Leveque, J.F. LeNest, A. Gandini and H. Cheradame, J. Power Sources, 14, 27 (1985).
8. M.Z.A. Munshi and B.B. Owens, this journal.
9. D.F. Shriver, S. Clancy, P.M. Blonsky and L.C. Hardy, Proc. 6th Riso Intn'l Symp., Denmark, 353 (1985).
10. R. Huq and G.C. Farrington, results to be published.

Table 1. Variation in the transport # of Li^+ against electrolyte thickness

System	Electrolyte thickness/μm	Transport # @ 100 C
8:1 PEO-LIAICl ₄	15	.50
8:1 PEO-LIAICl ₄	32	.49
8:1 PEO-LIAICl ₄	60	.50
8:1 PEO-LIAsF ₆	18	.56
8:1 PEO-LIAsF ₆	33	.54
8:1 PEO-LIAsF ₆	49	.54
8:1 PEO-LIPF ₆	12	.47
8:1 PEO-LIPF ₆	16	.47
8:1 PEO-LIPF ₆	37	.48
8:1 PEO-LICF ₃ SO ₃	8	.46
8:1 PEO-LICF ₃ SO ₃	23	.45
8:1 PEO-LICF ₃ SO ₃	56	.46
8:1 PEO-LIBF ₄	7	.38
8:1 PEO-LIBF ₄	19	.37
8:1 PEO-LIBF ₄	28	.40

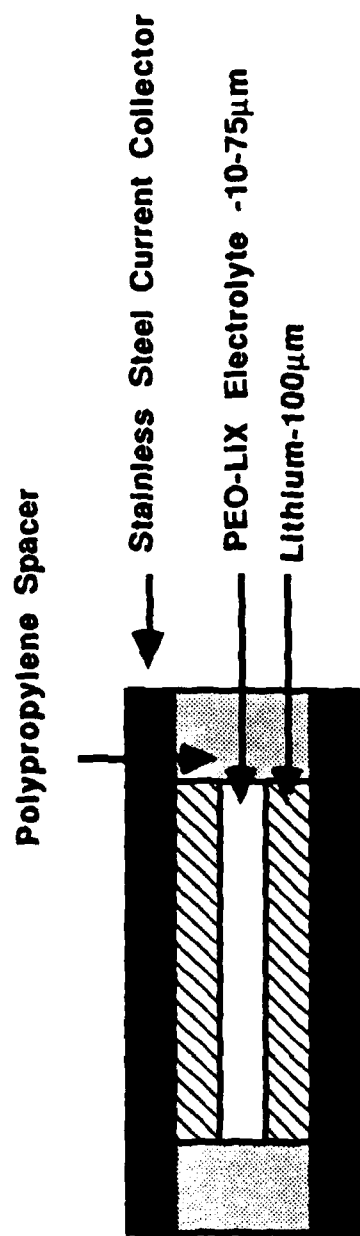


Figure 1. Schematic of the polarization cell

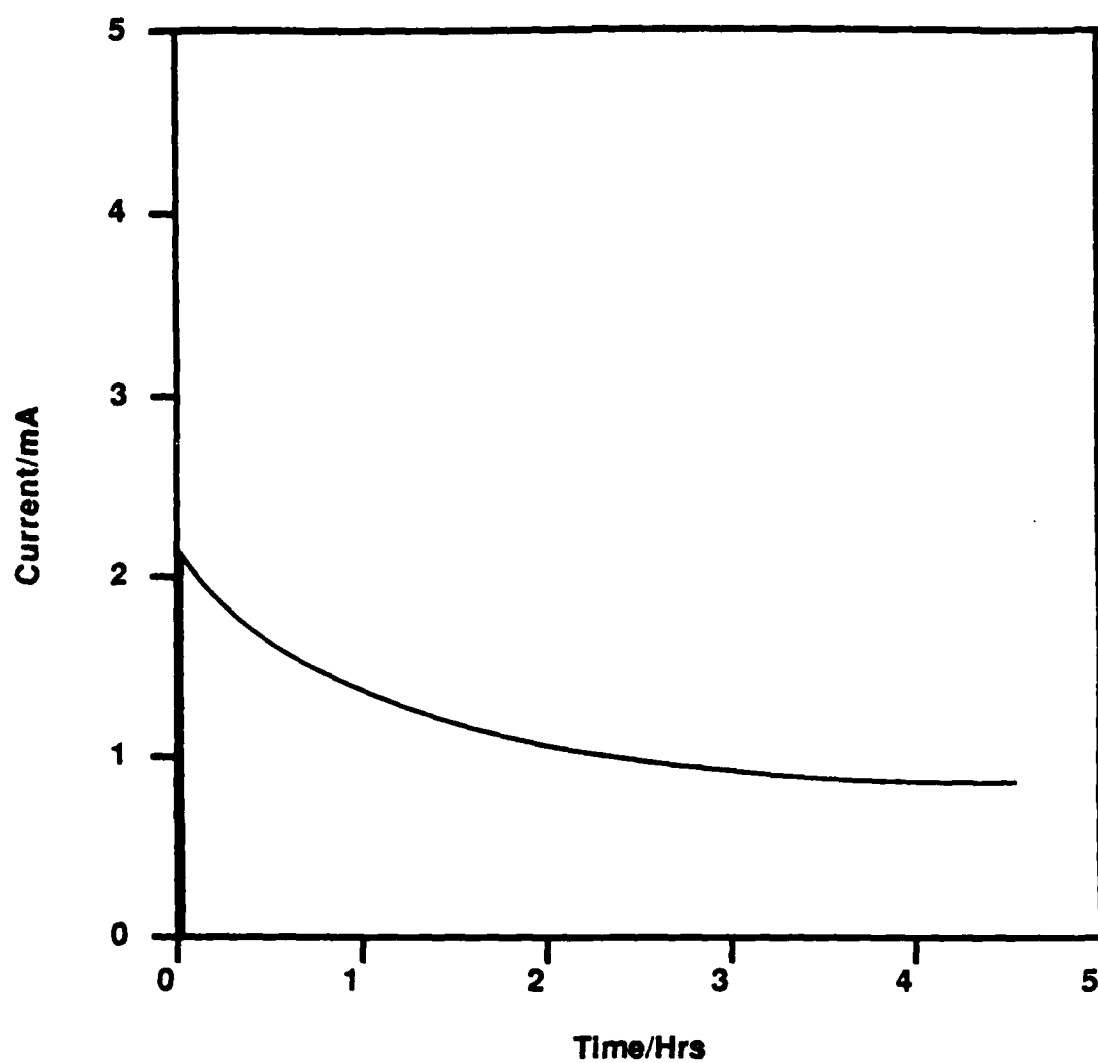


Figure 2. Typical variation in the cell current with time ; e.g. 8:1 PEO-LiCF₃SO₃
at 100°C.

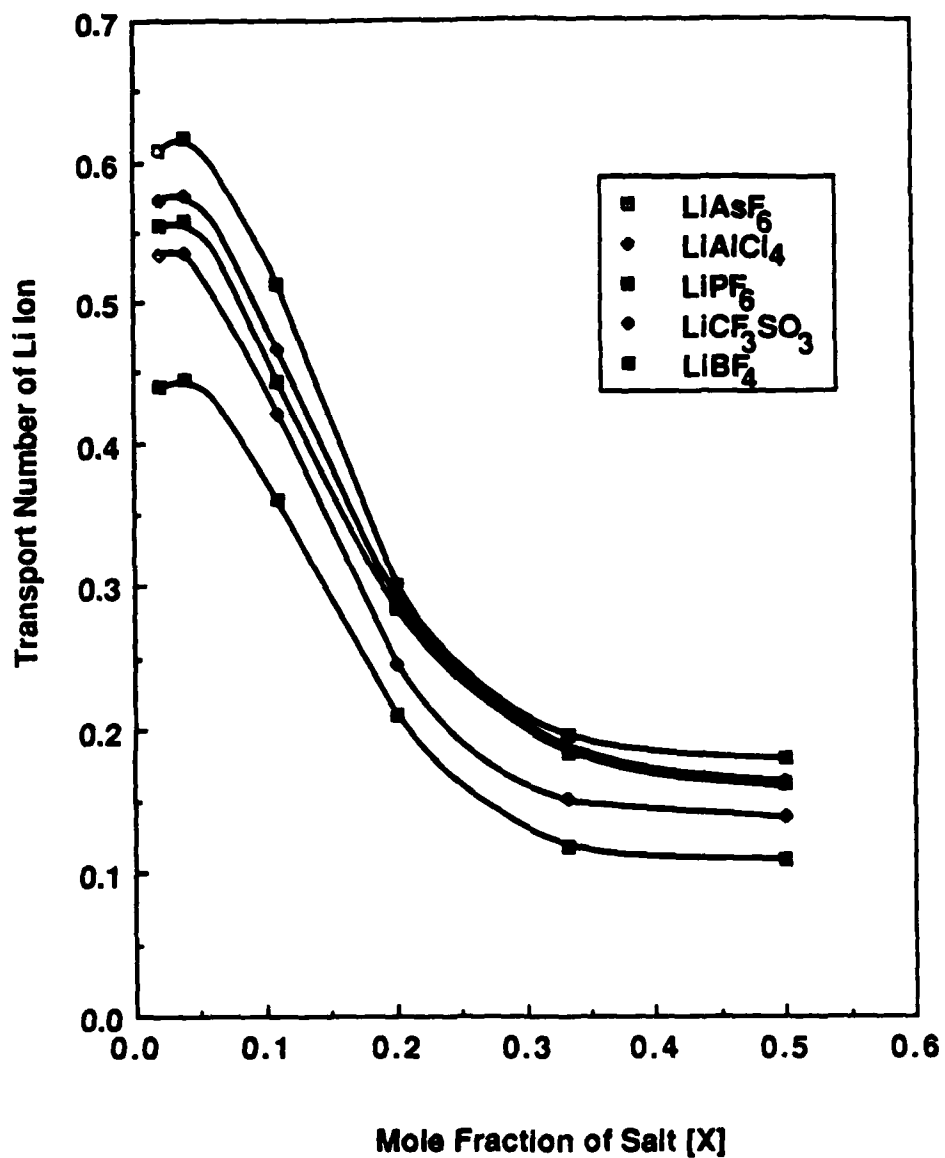


Figure 3. Variation in the Li transport number with mole fraction of salt.

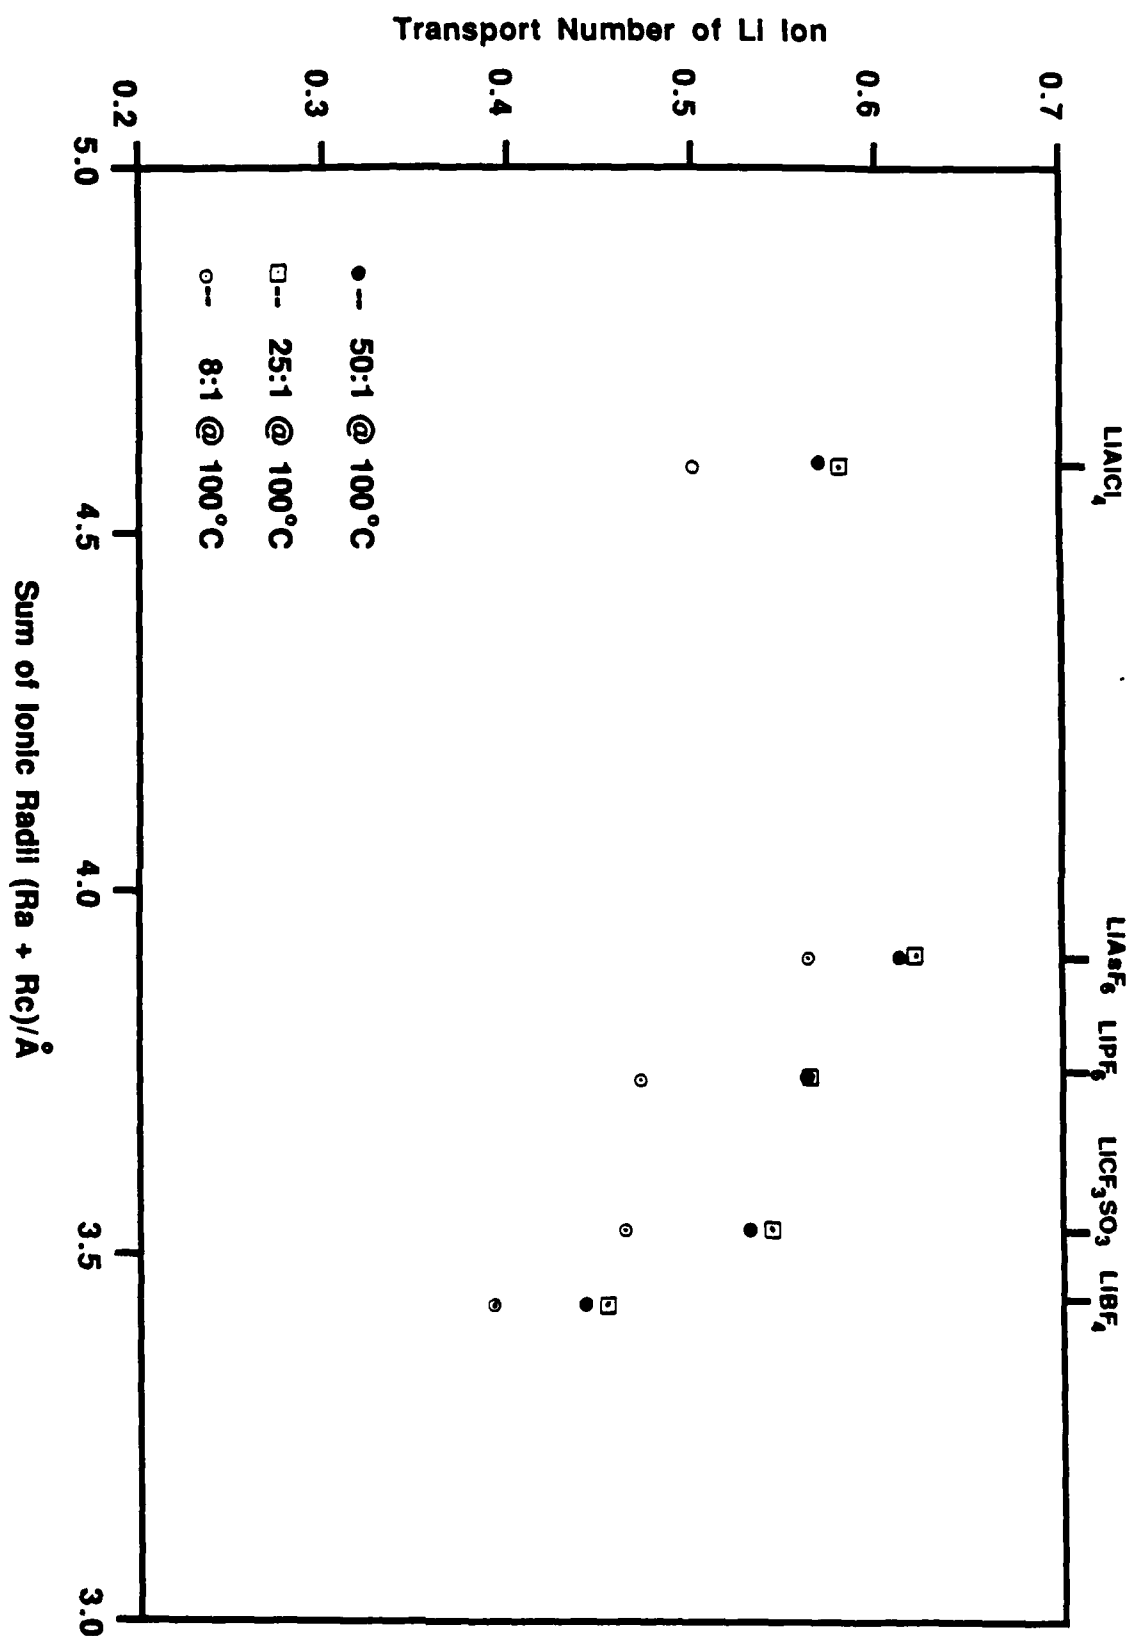


Figure 4. Variation of Li transport number with ionic radius of salts.

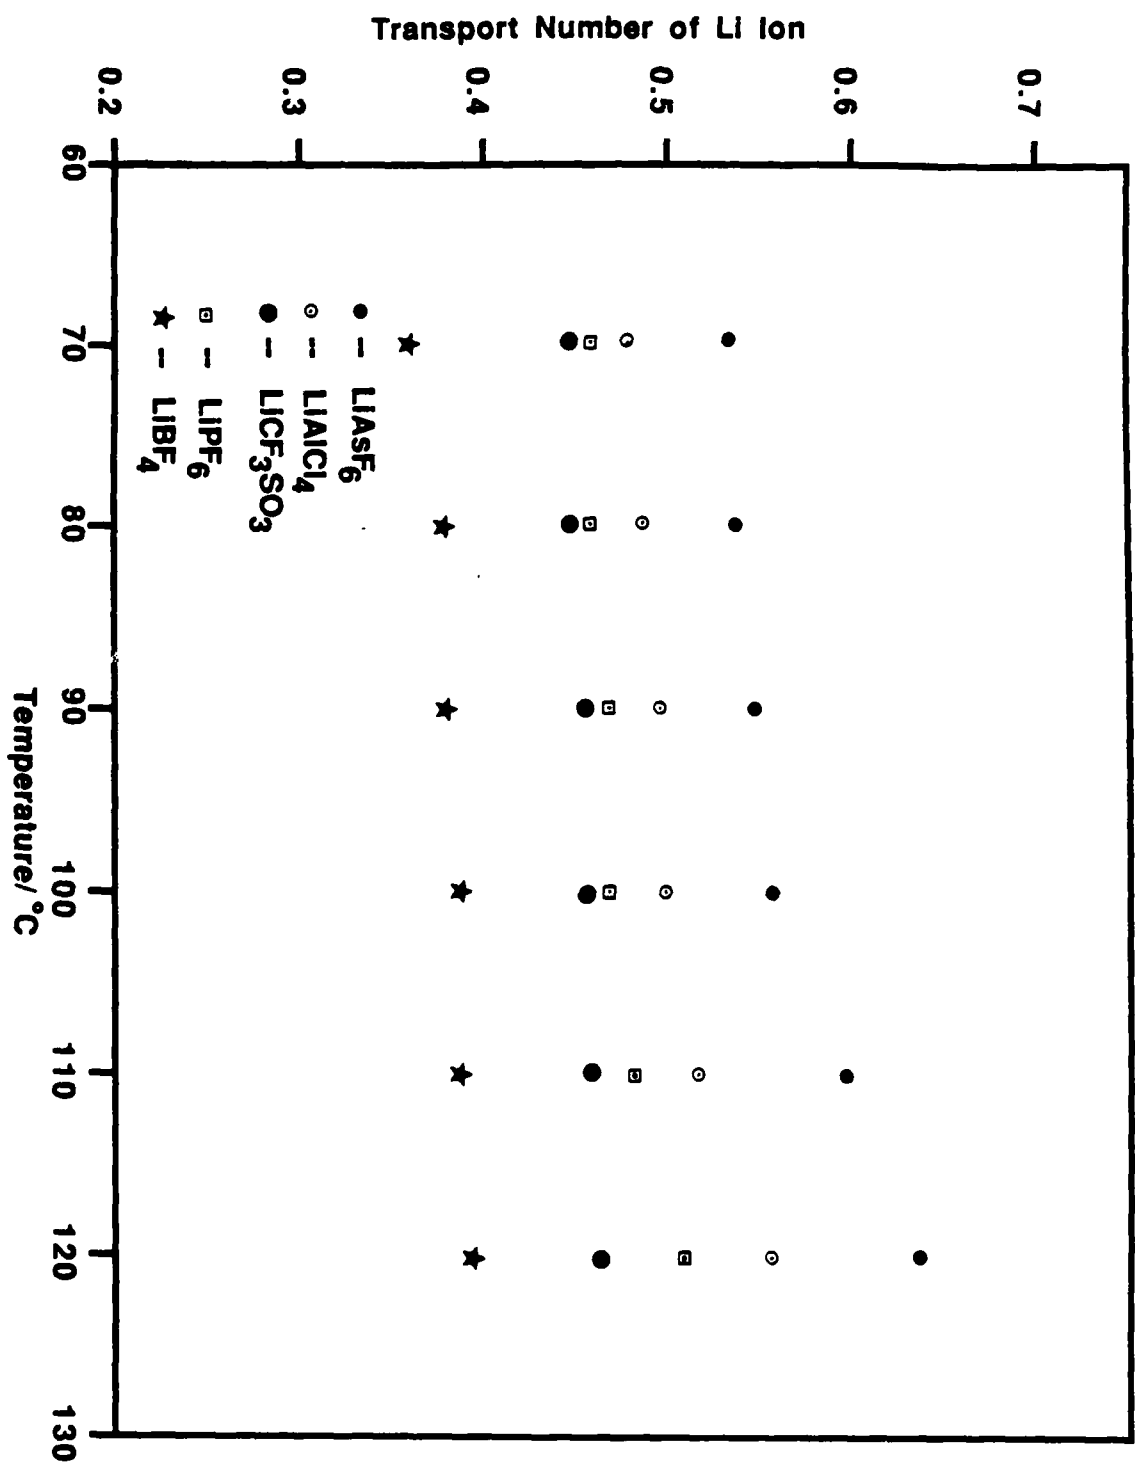


Figure 5. Variation of Li transport number with temperature for PEO-LiX system

Figure Captions

Figure 1. Schematic of the polarization cell

Figure 2. Typical variation in the cell current with time; e.g., 8:1
PEO-LiCF₃SO₃ at 100°C

Figure 3. Variation in the Li transport number with mole fraction of
salt

Figure 4. Variation of Li transport number with ionic radius of salts

Figure 5. Variation of Li transport number with temperature for PEO-LiX
system

END

DATE

FILMED

DTIC

JULY 88